

ARTICLE

DOI: 10.1038/s41467-017-01100-7

OPEN

Identification of catalytic sites in cobalt-nitrogen-carbon materials for the oxygen reduction reaction

Andrea Zitolo¹, Nastaran Ranjbar-Sahraie², Tzonka Mineva², Jingkun Li³, Qingying Jia³, Serban Stamatin⁴, George F. Harrington^{5,6}, Stephen Mathew Lyth^{7,8}, Petr Krtil⁴, Sanjeev Mukerjee³, Emiliano Fonda¹ & Frédéric Jaouen²

Single-atom catalysts with full utilization of metal centers can bridge the gap between molecular and solid-state catalysis. Metal-nitrogen-carbon materials prepared via pyrolysis are promising single-atom catalysts but often also comprise metallic particles. Here, we pyrolytically synthesize a Co-N-C material only comprising atomically dispersed cobalt ions and identify with X-ray absorption spectroscopy, magnetic susceptibility measurements and density functional theory the structure and electronic state of three porphyrinic moieties, CoN₄C₁₂, CoN₃C_{10,porp} and CoN₂C₅. The O₂ electro-reduction and *operando* X-ray absorption response are measured in acidic medium on Co-N-C and compared to those of a Fe-N-C catalyst prepared similarly. We show that cobalt moieties are unmodified from 0.0 to 1.0 V versus a reversible hydrogen electrode, while Fe-based moieties experience structural and electronic-state changes. On the basis of density functional theory analysis and established relationships between redox potential and O₂-adsorption strength, we conclude that cobalt-based moieties bind O₂ too weakly for efficient O₂ reduction.

¹Synchrotron SOLEIL, L'orme des Merisiers, BP 48 Saint Aubin, 91192 Gif-sur-Yvette, France. ²Institut Charles Gerhardt Montpellier, UMR 5253, CNRS, Université Montpellier, Place Eugène Bataillon, 34095 Montpellier cedex 5, France. ³Department of Chemistry and Chemical Biology, Northeastern University, Boston, MA 02115, USA. ⁴J. Heyrovsky Institute of Physical Chemistry, Academy of Sciences of the Czech Republic, Prague, 18223, Czech Republic. ⁵Center for Co-Evolutional Social Systems, Kyushu University, 744 Motooka, Nishi-ku, Fukuoka 819-0395, Japan. ⁶Department of Materials Science and Engineering, Massachusetts Institute of Technology, 77 Massachusetts Avenue, Cambridge, MA 02139, USA. ⁷International Institute for Carbon-Neutral Energy Research (WPI-I2CNER), Kyushu University, 744 Motooka, Nishi-ku, Fukuoka 819-0395, Japan. ⁸Energy2050, Department of Mechanical Engineering, University of Sheffield, The Arts Tower, Sheffield S10 2TN, UK. Correspondence and requests for materials should be addressed to A.Z. (email: andrea.zitolo@synchrotron-soleil.fr) or to F.J. (email: frederic.jaouen@umontpellier.fr)

The transition from fossil to renewable energies is necessary to meet the rising energy demand while minimizing anthropogenic climate change and urban pollution^{1–3}. Electrochemical energy conversion will play an increasing role for the storage of renewable electricity, production of fuels and their conversion into electricity. Hydrogen is an interesting energy vector since it can be produced via water electrolysis (hydrogen evolution reaction, HER) and later oxidized in H₂/air fuel cells to reform water and electricity on demand (hydrogen oxidation reaction, HOR). However, the electrochemical oxygen reactions (oxygen reduction reaction (ORR) and oxygen evolution reaction (OER)) are slow, limiting the roundtrip efficiency⁴. While acidic electrolytes are more restrictive than alkaline ones regarding the breadth of catalysts that may be stable under ORR/OER conditions, the advent of highly conductive and stable proton exchange membranes (PEM) has hitherto favoured the development of acidic fuel cells and electrolyzers. Their major drawback is, however, the need for platinum-group metals to catalyze the ORR and OER.

Following the pioneering report of Jasinski on the ORR activity of cobalt phthalocyanine⁵, advanced Metal–N–C materials have since 1989 been prepared by pyrolyzing separate metal, nitrogen and carbon precursors⁶. Although the activity and durability of such catalysts have been improved^{7–11}, the identification of the

active-site structure has lagged behind due to the non-crystallographic order of metal atoms in the most active sites and the simultaneous presence of crystalline metal phases. Metal ions coordinated with pyridinic nitrogen atoms embedded in a graphene matrix with hexagonal atomic arrangement, such as the MeN₄C₁₀ moiety, have for a long time been viewed as the most probable site structure^{12–18}. Other studies hypothesized moieties integrated in disordered carbon sheets involving non-hexagonal rings, such as the MeN₄C₁₂ moiety^{19, 20}. Calle-Vallejo et al.²¹ investigated with density functional theory (DFT) the adsorption energy of oxygen intermediates on MeN₄C₁₂ and MeN₄C₁₀ moieties, revealing differences up to 0.7 eV. This highlights the importance of precisely determining the local site structures in Me–N–C materials for deciphering their reactivity.

Using X-ray absorption near-edge structure (XANES) spectroscopy we recently identified the active-site structure in pyrolyzed Fe–N–C catalysts as being a porphyrin-like FeN₄C₁₂ moiety, in contrast with FeN₄C₁₀ or FeN₂₊₂C₄₊₄ moieties previously assumed²². The formation of FeN₄C₁₂ moieties requires a strongly-disordered host material, in line with experimental observations^{9, 23}. Although moieties present in Fe–N–C materials are now better described^{22, 24–26}, active sites in Co–N–C materials are still poorly identified. Co–N–C catalysts are ORR-active and advantageous vs. Fe–N–C since they produce less radical oxygen

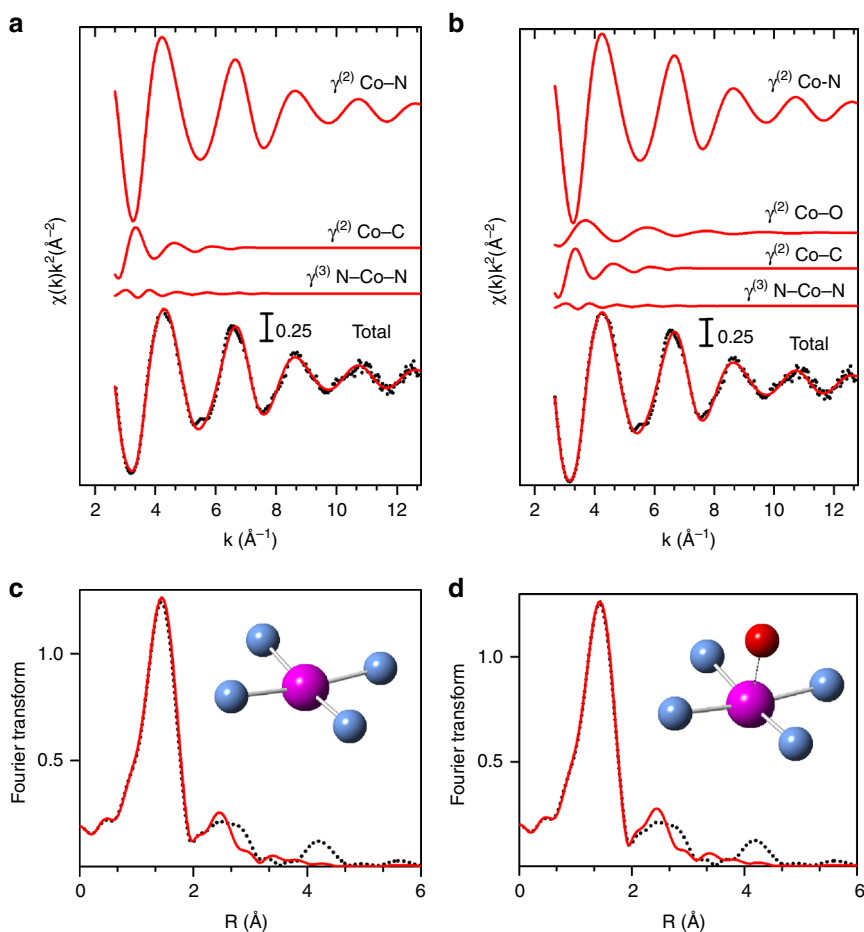


Fig. 1 Co K-edge EXAFS analysis. Spectra of Co_{0.5} with a CoN₄ moiety having zero (left) or one (right) oxygen atom in the axial direction. Cobalt, nitrogen and oxygen atoms are represented in purple, blue and red, respectively (carbon atoms in the second coordination sphere are not represented). **a, b** Curves from top to bottom: Co–N, Co–O and Co–C $\gamma^{(2)}$ two-body signals and the N–Co–N $\gamma^{(3)}$ three-body signal included in the fit, the total signal (red line) superimposed on the experimental one (black dots). **c, d** the fit in the Fourier-transformed space. No phase-shift correction was applied to the Fourier transforms

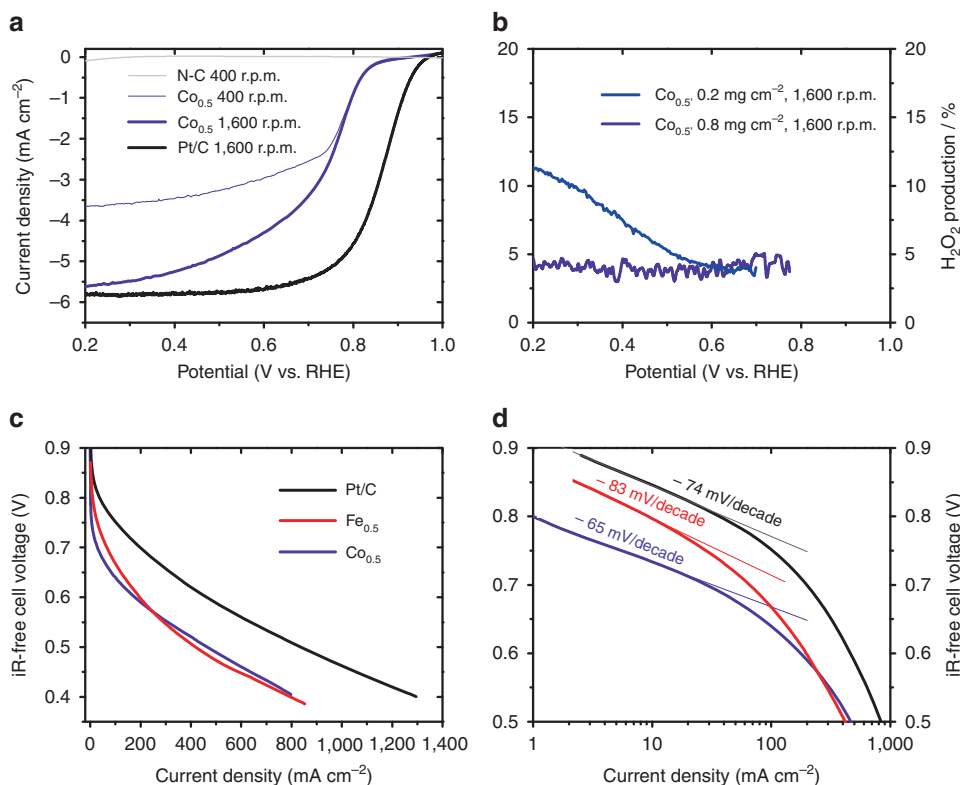


Fig. 2 ORR electrochemical characterization. Measurements of $\text{Co}_{0.5}$, $\text{Fe}_{0.5}$, N-C and a Pt/C benchmark catalyst. Upper panels are RRDE measurements at various rotation rates and loadings performed in O_2 -saturated 0.1 M H_2SO_4 aqueous solution. **a** ORR current density at the disk. The total catalyst loading for $\text{Co}_{0.5}$, N-C and Pt/C (5 wt% Pt/C) was 0.8 mg cm^{-2} . **b** % H_2O_2 measured during ORR at the ring. The total catalyst loading for $\text{Co}_{0.5}$ was 0.8 or 0.2 mg cm^{-2} . Lower panels are iR-corrected PEMFC polarization curves with $\text{Co}_{0.5}$, $\text{Fe}_{0.5}$ or Pt/C at the cathode, presented in linear scale **c** and semi-logarithmic scale **d**. The fuel cell temperature was 80°C , pure H_2 and O_2 gases were fully humidified at the cell temperature, the gauge pressure was 1 bar. The cathode catalyst loading for $\text{Co}_{0.5}$ and $\text{Fe}_{0.5}$ was 4 mg cm^{-2} ($60 \mu\text{g}_{\text{metal}}$ per cm^2). For Pt/C at the cathode, 5% Pt/C was diluted to 1% Pt with uncatalysed Vulcan carbon black, and 4 mg cm^{-2} of 1% Pt/C ($40 \mu\text{g}_{\text{Pt}}$ per cm^2) deposited

species, leading to improved fuel cell durability²⁷. They also have recently been reported to catalyze the HER^{28, 29}. The existence of atomically dispersed cobalt atoms on N-doped graphene layers has been unambiguously demonstrated by mass spectroscopy and scanning transmission electron microscopy (STEM)^{29, 30}. DFT investigations also concluded the energetically favoured formation of CoN_xC_y moieties^{20, 21, 31–34}. Extended X-ray absorption fine structure (EXAFS), previously used to investigate CoN_xC_y moieties^{35–37}, is insufficiently sensitive to the spatial arrangement of coordinating light elements surrounding the absorbing cobalt nucleus.

The present study identifies with XANES the detailed structure of CoN_xC_y moieties in a Co–N–C catalyst free of cobalt particles. Similar to Fe–N–C, the porphyrin-like $\text{CoN}_4\text{C}_{12}$ moiety is found to be the likeliest structure. In contrast to Fe–N–C, defective cobalt porphyrinic moieties are also viable candidates. Also metal-discriminating, *operando* XANES spectroscopy shows no change with electrochemical potential in the entire ORR range for Co–N–C, but a major change for Fe–N–C. The spectral change for Fe–N–C is correlated with a change of oxidation state in that potential region, while the lack of spectral change for cobalt is correlated with an unmodified oxidation state in that potential region.

Results

Absence of Co–Co bonds in $\text{Co}_{0.5}$ evidenced with EXAFS and TEM. We synthesized a Co–N–C catalyst with the same approach

developed for preparing Fe–N–C catalysts comprising only FeN_xC_y moieties, and labeled it $\text{Co}_{0.5}$, with 0.5% Co in the catalyst precursor before pyrolysis (see Methods).²² The EXAFS spectrum of $\text{Co}_{0.5}$ was analyzed assuming a variable number of nitrogen ligands in the equatorial plane and additional oxygen atoms in the axial position. The best-fit analysis is shown in Fig. 1, revealing 4- and/or 5-fold coordination structures. No Co–Co backscattering signal was needed to obtain an excellent fit. The dominant contribution to the EXAFS signal is given by the Co–N bonds of the first coordination shell (top of Fig. 1). The lower panels show the corresponding fits in the Fourier-transformed space. The peak at 1.45 \AA is associated with the Co–N and/or Co–O first-shell contributions while the peak at 2.44 \AA is due to Co–C. The structural parameters obtained from the fitting are reported in Supplementary Table 1. The Co–N distance, $1.95\text{--}1.96 \text{ \AA}$, agrees with values determined by DFT for cobaltous-porphyrins.³⁸ However, the EXAFS experimental data can be reproduced with the same accuracy by a CoN_4 or an O- CoN_4 structure, as reported for $\text{Fe}_{0.5}$ (ref. 22). Moreover, the uncertainty on the nitrogen coordination number (Supplementary Table 1) leaves room for hypothesizing moieties with a lower coordination, as investigated later in this study. The absence of metallic Co–Co bonds in $\text{Co}_{0.5}$ was independently confirmed by TEM (Supplementary Fig. 1). The selected area electron diffraction (SAED) pattern shows only broad rings, as expected for amorphous carbon. No sign of reflections originating from metallic particles were observed, and no evidence of particles was found in the images. Multiple areas of the sample were analyzed, and the

images and SAED pattern in Supplementary Fig. 1 are representative.

Electrocatalytic properties of Co_{0.5} towards the ORR. The ORR activity and selectivity of Co_{0.5} was then investigated with a rotating ring disk electrode (RRDE) in acid medium (Fig. 2a). The ORR current density at 0.8 V vs. a reversible hydrogen electrode (RHE) is 0.9 mA cm⁻² for a loading of 800 μg cm⁻² (12 μg_{Co} cm⁻²), which compares well with state of art Co–N–C catalysts in acid medium, in spite of low cobalt content in Co_{0.5} (refs 39–41). The Pt/C catalyst reaches 1.0 mA cm⁻² at 0.91 V vs. RHE, and its higher activity is due to its higher atom-specific ORR activity (the higher Pt loading, 40 μg_{Pt} cm⁻², resulting in identical number of metal atoms per cm² as for cobalt, due to the 3.3 times higher molar mass of Pt vs. Co).

Regarding selectivity, the % peroxide released by Co_{0.5} during ORR at 0.5–0.8 V vs. RHE is 3–5 % in 0.1 M H₂SO₄ at a loading of 800 μg cm⁻² (Fig. 2b). Co_{0.5} is thus less selective to water formation than Fe_{0.5}, for which we measured <0.5 % H₂O₂ in acid, at equal catalyst loading.²² The peroxide production was also measured at a lower loading, since it has been reported that, for some Fe–N–C catalysts, this can result in greatly increased detection of H₂O₂ (ref. 41). The % H₂O₂ released by Co_{0.5}, however, only increased up to 11% at 200 μg cm⁻² (Fig. 2b). By analogy with what is known for unpyrolyzed Metal–N₄ macrocycles, this result may be explained by the generally higher formal potential of Metal^{III}/Metal^{II} for cobalt vs. iron macrocycles, leading to weaker interaction with oxygen intermediates, including H₂O₂ (ref. 42). Square-wave-voltammetry in acidic medium supports this possible explanation, identifying redox-peak positions at 1.25 V and 0.75 V vs. RHE for Co_{0.5} and Fe_{0.5}, respectively (Supplementary Fig. 2). Although Co–N–C catalysts typically release more peroxide during the ORR, subsequent reactions between H₂O₂ and MeN_xC_y moieties produce less radical oxygen species on cobalt- than iron-centers, which is beneficial for fuel cell durability²⁷. Also, the insignificant ORR activity in acidic medium of N–C (Fig. 2a) means that the cobalt moieties are the most active-site for ORR in Co_{0.5}. This catalyst was then investigated in PEM fuel cell and compared to Fe_{0.5} and Pt/C (Fig. 2c, d). For comparison, we prepared a Pt-based cathode with similar metal-site density (1% Pt/C) and similar thickness as Co_{0.5} or Fe_{0.5} cathodes. For carbon-rich catalysts, the thickness is set by the catalyst loading, here 4 mg cm⁻², typically resulting in 80–100-μm-thick layers¹⁰. Although the ORR activity at 0.8 V of Co_{0.5} is lower than that of Fe_{0.5} (Fig. 2d), the lower apparent Tafel slope (TS) observed with Co_{0.5} at high potential leads to a higher power performance at E < 0.55 V. The apparent TS of 83 mV/decade for Fe_{0.5} probably results from the outcome of an intrinsic TS with value > 83 mV per decade combined with the potential-dependence of the Fe(III) and Fe(II) coverages⁴³, with Fe(III) blocking the ORR due to overly strong O₂ adsorption. A similar phenomenon occurs for Pt, switching from surface-oxidized state to a surface free of oxygen adsorbates at ~0.8 V vs. RHE^{44, 45}. In contrast, Co_{0.5} does not change oxidation state throughout the ORR region (Supplementary Fig. 2) and the TS-value of 65 mV per decade observed at high potential is, therefore, intrinsic to the ORR mechanism on CoN_xC_y moieties. Overall, and for similar cathode thickness, the gap between the curves for 1% Pt/C and Co_{0.5} or Fe_{0.5} is only a factor two at 0.6 V. A key issue is that, while Pt can be deposited as nanoparticles up to 50 wt% on carbon, the ORR activity of Metal–N–C materials levels off at 2–3 wt% metal⁴⁶. Further work is thus needed to (i) improve reactant transport in thick Me–N–C electrodes, (ii) increase the number of active sites or (iii) their turnover frequency. The latter two tasks

require identifying the structure of active moieties, object of the present study.

Structural identification of Co-moieties in Co_{0.5} by XANES. To overcome the limitations of EXAFS, we resorted to XANES, which is more sensitive to the geometrical arrangement of atoms around the photo-absorber. Our XANES analysis was first validated with cobalt phthalocyanine (Co(II)Pc). The agreement between experimental and calculated spectra of Co(II)Pc is excellent in the whole energy range (Supplementary Fig. 3). For this fit, the square residual function, R_{sq} (Methods section) is 1.06. The optimized structure resulted in a Co–N distance of 1.90(2) Å, which agrees with an X-ray diffraction determination⁴⁷. We then calculated the Co K-edge XANES spectra of various CoN_xC_y candidate sites for Co_{0.5}, including structures previously investigated with DFT^{20, 31–34}. Some of these clusters are depicted in Supplementary Fig. 4 together with the results of the fitting procedure. Supplementary Fig. 4a, c report the XANES fitting performed assuming a CoN₄C₁₀ moiety enclosed in a graphene plane and a CoN₂₊₂C₄₊₄ moiety bridging two graphene planes, respectively. For the calculations, only the in-plane distances between cobalt and nitrogen atoms were allowed to vary. For these hypothetical sites, the fit between experimental and calculated XANES spectra is unsatisfactory (R_{sq} = 2.97 and 2.81, respectively) and the fit quality was little improved by adding an axial oxygen (Supplementary Fig. 4b, d). The disordered arrangement of nitrogen and carbon atoms surrounding cobalt ions has been recently revealed by STEM for another Co–N–C catalyst²⁹. This suggests that the arrangement of carbon atoms around cobalt ions is different from that in graphene.

We then considered two defective sites derived from CoN₄C₁₀, namely pyridinic CoN₃C_{10,pyr} and CoN₂C₈ (Supplementary Fig. 5a, c) and two defective sites derived from CoN₂₊₂C₄₊₄, namely CoN₂₊₁C₄₊₃ and CoN₂C₄ (Supplementary Fig. 5e, g). None of these four pyridinic-defective candidate sites correctly reproduced the experimental XANES spectrum of Co_{0.5}. Again, the addition of an O₂ molecule in end-on mode did not improve much the fit quality (Supplementary Fig. 5b, d, f, h). The structural parameters obtained from these analyses are summarized in Supplementary Table 2.

We then considered a cobalt moiety based on a porphyrinic architecture, analogous to that found for the Fe-based active-site geometry in Fe_{0.5} (ref. 22). Fig. 3a, b show the XANES analyses performed on the square-planar CoN₄C₁₂ moiety, with and without an axial O₂ adsorbed end-on. These fits show an excellent agreement between experimental and theoretical spectra and correspond to a moiety where the cobalt ion is coordinated in-plane by four nitrogen atoms at 1.96–1.97 Å, and possibly by one oxygen molecule at 2.23 Å (Table 1, rows 1 and 2). Two defective sites, derived from the porphyrinic CoN₄C₁₂ moiety by subtracting one or two nitrogen atoms (porphyrinic CoN₃C_{10,porp} and CoN₂C₅ model sites), also correctly reproduce the experimental spectrum (Fig. 3c, e, respectively). For the CoN₃C_{10,porp} motif, the XANES analysis resulted in a Co–N bond length of 1.96 Å when O₂-free, and 1.99 Å when O₂ is adsorbed end-on without out-of-plane displacement of cobalt (Table 1, rows 3 and 4). The XANES analysis also revealed the CoN₂C₅ edge-defect, representing a halved porphyrinic moiety, binding O₂ end-on with a Co–O bond length of 1.90 Å with O₂ in the same plane as the CoN₂C₅ motif (Fig. 3e, f and Table 1, rows 5 and 6). For the CoN₂C₅ motif only, the bound O₂ molecule was necessary to reach a good fit (R_{sq}-value of 1.12–1.16, Table 1). For the CoN₄C₁₂ and CoN₃C_{10,porp} moieties (with or without adsorbed O₂), the Co–N bond lengths determined by XANES and EXAFS are in good agreement, and so

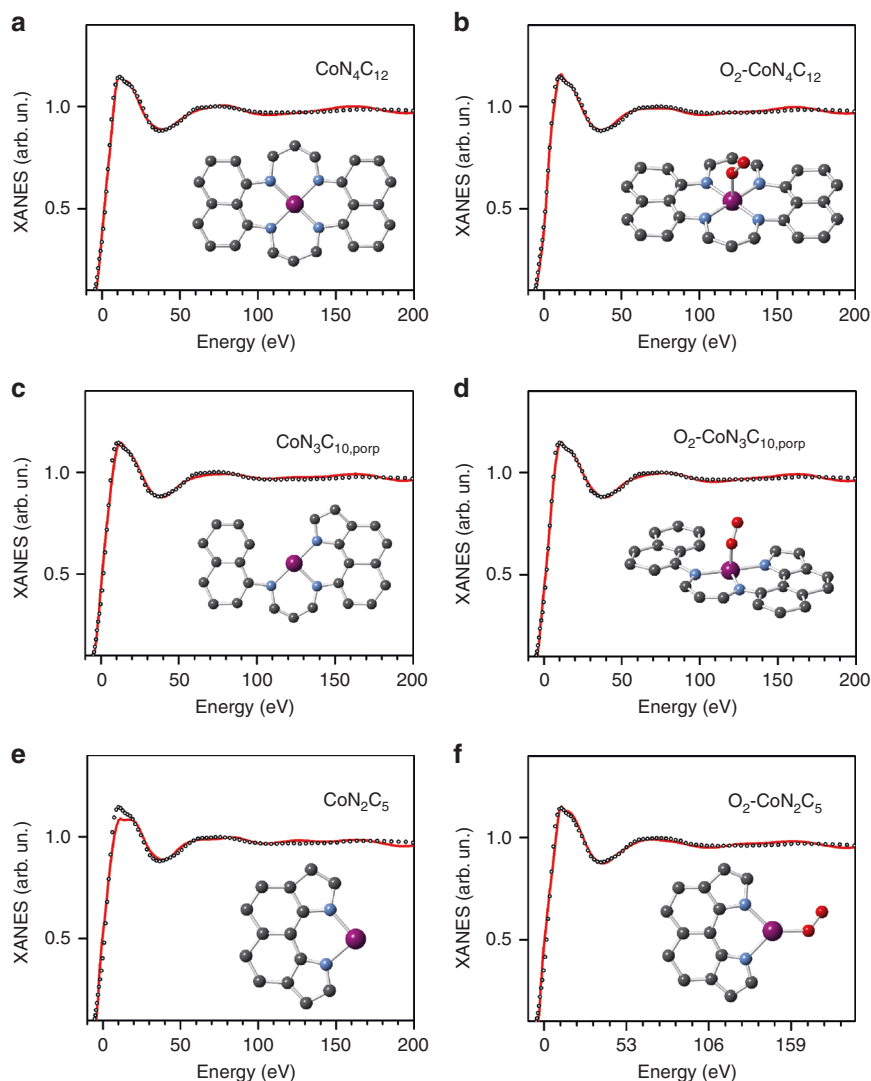


Fig. 3 Experiment versus theory. **a–f** Comparison between the K-edge XANES experimental spectrum of $\text{Co}_{0.5}$ (black hollow circles) and the theoretical spectrum calculated with the depicted structures (solid red lines). Cobalt, nitrogen, oxygen and carbon atoms are represented in purple, blue, red and gray, respectively

is the case for the CoN_2C_5 moiety free of adsorbed O_2 (Table 1 and Supplementary Table 1).

The energy of formation and O_2 adsorption energy were then calculated by DFT-D approach for the possible sites identified by XANES analysis, namely $\text{CoN}_4\text{C}_{12}$, $\text{CoN}_3\text{C}_{10,\text{porp}}$ and CoN_2C_5 , and the results were compared to those obtained for the $\text{CoN}_4\text{C}_{10}$ pyridinic moiety (Supplementary Fig. 6). The optimized bond distances for the above-mentioned porphyrinic sites, with and without a dioxygen molecule adsorbed in end-on mode, follow the trends of bond distances determined by EXAFS and XANES (Supplementary Table 3). The stability of these porphyrinic defective motifs is assessed by the Co(II) binding energy, -6.8 to -7.5 eV for the ground states, comparable to -8.2 eV obtained for $\text{CoN}_4\text{C}_{10}$ (Supplementary Table 4). Moreover, our DFT-D results reveal that the adsorption of an O_2 molecule results in the displacement of the cobalt ion by 0.4 and 0.5 Å above the plane for $\text{CoN}_3\text{C}_{10,\text{porp}}$ and CoN_2C_5 , respectively. The O_2 adsorption energies in the ground-state structures are -0.80 , -1.23 and -1.26 eV for $\text{CoN}_4\text{C}_{12}$, $\text{CoN}_3\text{C}_{10,\text{porp}}$ and CoN_2C_5 , respectively. This is comparable to the O_2 adsorption energies for the ground state of the $\text{CoN}_4\text{C}_{10}$ site, -0.97 eV. Although O_2 adsorbs on all

cobalt moieties, the obtained adsorption energies are, however, significantly smaller than those of the $\text{FeN}_4\text{C}_{10}$ and $\text{FeN}_4\text{C}_{12}$ moieties in ground state, -1.83 and -1.84 eV, respectively (Supporting Information of ref. 22). This indicates that cobalt binds O_2 more weakly compared to iron-based moieties. Due to the lower experimental ORR activity of $\text{Co}_{0.5}$ vs. $\text{Fe}_{0.5}$ (Fig. 2d) one can unambiguously conclude that cobalt moieties are situated on the weak-binding side of a volcano plot. While no definitive conclusion can be made on the volcano-plot position of iron moieties in $\text{Fe}_{0.5}$ only from the present work (the weak and strong binding branches being both possible), yet unpublished work on $\text{Fe}_{0.5}$ post-treated with H_2O_2 suggests that $\text{Fe}_{0.5}$ is also positioned on the weak binding side of a volcano plot. The weaker binding of O_2 (and thus of H_2O_2 , via scaling relationships) by CoN_xC_y moieties also explains the higher amount of peroxide detected by RRDE for Co–N–C vs. Fe–N–C, as reported above. The O_2 adsorption energy of molecular cobalt catalysts is often weaker than desired for an ideal metal-centered moiety,⁴² and the same conclusion is made from the present combined experimental and theoretical study for the pyrolyzed $\text{Co}_{0.5}$ catalyst. Hence, cobalt-moieties with the highest calculated O_2 adsorption energy should

Table 1 XANES structural parameters for porphyrinic cobalt moieties

Row nbr.	Moiety	Co-N/Å	Co-O/Å	Bending/°	R _{sq}
CoN₄C₁₂					
1	4-fold	1.96 (2)	—	—	1.12
2	5-fold	1.97 (3)	2.23 (5)	33 (6)	1.08
CoN₃C_{10,porp}					
3	3-fold	1.96 (3)	—	—	1.16
4	4-fold	1.99 (3)	1.86 (4)	32 (7)	1.05
CoN₂C₅					
5	2-fold	1.96 (3)	—	—	1.98
6	3-fold	2.01 (4)	1.90 (4)	50 (5)	1.13

Abbreviation: XANES, X-ray absorption near-edge structure
 Best-fit structural parameters obtained from the analysis of the XANES spectrum of Co_{0.5} performed on the structures proposed in this work and depicted in Fig. 3. Bending is the angle between the Co-O vector and the O-O bond and R_{sq} is the residual function. Errors are given in parentheses

be the most active ones, which gives the following expected ORR turnover frequency ranking CoN₂C₅ > CoN₃C_{10,porp} > CoN₄C₁₂. To better assess which moieties may be present in Co_{0.5}, we measured the magnetic susceptibility of Co_{0.5} and N-C with superconducting quantum interference device (Supplementary Fig. 7). The plot of the inverse of the magnetic molar susceptibility χ_m of Co_{0.5} is linear with temperature (inset of Supplementary Fig. 7), as expected for Curie-Weiss paramagnetism. The positive intercept at 0 K leads to a negative Curie-Weiss temperature of -0.36 K, signifying weak antiferromagnetic interaction between magnetic moments⁴⁸. The value of the slope $1/\chi_m = f(T)$ yields a magnetic moment $\mu_{\text{eff}} = 3.52$ Bohr magnetons (μ_B), averaged on all cobalt moieties in Co_{0.5}. For the first-row transition metals, to the first approximation, only the spin contribution to the effective magnetic moment can be considered ($\mu_{\text{eff}} = 2 \mu_B \sqrt{(s^2 + s)}$) leading to $s_{\text{average}} = 1.33$ in Co_{0.5}, where s_{average} is the spin density averaged on all cobalt moieties present in Co_{0.5}. According to the DFT spin density analysis and selecting the three best candidates on the basis of EXAFS and XANES analysis (Supplementary Table 4, CoN₄C₁₂, CoN₃C_{10,porp} and O₂-CoN₂C₅ in their ground state, spin density of cobalt of 0.88, 0.58 and 1.83, respectively), one can propose that Co_{0.5} contains for example CoN₄C₁₂ and O₂-CoN₂C₅ in a 53%/47% distribution, or CoN₃C_{10,porp} and O₂-CoN₂C₅ in a 40%/60% distribution. Both distributions result in a theoretical s_{average} value of 1.33, similar to the experimental value (Supplementary Table 5). Considering only these three motifs, the fraction of O₂-CoN₂C₅ sites must be in the range of 47–60%, the remainder being split between CoN₄C₁₂ and CoN₃C_{10,porp} sites.

We recently demonstrated that the porphyrinic FeN₄C₁₂ moiety with one or two axial ligands matched the XANES experimental spectrum of Fe_{0.5} and other Fe-based catalysts²². Since defective Fe-porphyrinic moieties were not investigated in that study, we extended here the XANES analysis of Fe_{0.5} in order to investigate whether such Fe-based moieties could also match the experimental XANES spectrum of Fe_{0.5}. The analyses are shown in Supplementary Fig. 8 for FeN₃C_{10,porp} and FeN₂C₅. While O₂-FeN₃C_{10,porp} reproduces the general features of the spectrum, the fit quality is poorer than that obtained with O₂-FeN₄C₁₂ (Fig. 5e, f in ref. 22). Although this does not preclude the existence of FeN₃C_{10,porp} moieties in Fe_{0.5}, they may only represent a minor iron fraction. The present study therefore suggests that the structural disparity of MeN_xC_y moieties is larger in Co-N-C than Fe-N-C materials. Support for this is also provided by square-wave voltammetry (SWV) revealing a broader peak for Co_{0.5} (Supplementary Fig. 2).

Operando XANES signatures of Co- and Fe-moieties during ORR. We then investigated the behavior of Co- and Fe-based moieties in *operando* conditions. Figure 4a shows the normalized *operando* XANES spectra recorded at ORR potential range for Co_{0.5} in acid medium and Fig. 4b shows the same type of data for Fe_{0.5}. Although the latter show a large change with electrochemical potential, similar to a previous report by Mukerjee's group on other Fe catalysts⁴³, the magnitude of the change is insignificant for Co_{0.5} in the ORR region, even on the differential $\Delta\mu$ spectra (inset of Fig. 4a). The potential dependence of the XANES spectra observed on Fe_{0.5} in N₂-saturated electrolyte supports the fact that the XANES variability is primarily controlled by the electrochemical potential, while the adsorption of O₂ or oxygen intermediates has only a minor effect (Fig. 4d). The spectral changes observed in Fig. 4b probably result not only from a change in oxidation state, which would a priori only shift the edge position of the XANES spectra, but also from deeper structural changes and reorganization of the N (or C) ligands, as proposed in ref. 26 and/or an Fe(II) low-to-high spin-crossover⁴⁹. SWV (Supplementary Fig. 2) shows that, while Fe_{0.5} displays a clear peak at 0.75 V vs. RHE in acidic medium, Co_{0.5} did not show any signal in the 0–1 V region, but instead shows a redox transition at 1.25 V vs. RHE. This largely explains the different potential-dependences of the XANES spectra recorded in the ORR region for Fe_{0.5} and Co_{0.5}. In addition, the redox potential observed for Fe_{0.5} corresponds to its onset potential for the ORR (see Fig. 3b in ref. 22). It is however surprising that the XANES spectra of Fe_{0.5} are still changing below 0.6 V vs. RHE, while most Fe ions should already be in +II oxidation state. Spin-state or conformation changes may still be occurring below 0.6 V.

The very different position of the redox peak for Fe_{0.5} and Co_{0.5} experimentally supports the fact that O₂ adsorption on cobalt moieties is much weaker than on iron moieties. Linear relationships between the Me(III)/Me(II) redox potential and the adsorption energy for O₂ have clearly been established for various macrocycles comprising first-row transition metals (Fig. 3 in ref. 42). On this basis, the experimentally-determined relative positions of the redox peak for Fe_{0.5} and Co_{0.5} (0.75 and 1.25 V vs. RHE) are in line with our DFT calculations that predict O₂ adsorption energies of ~-1.8 eV for FeN₄C₁₂ and -0.8 to -1.2 eV for the porphyrinic Co-moieties.

Comparative *operando* XANES spectra collected under O₂ and N₂ provide additional insights in the reactivity of the active sites. Fig. 4c, d show the XANES spectra measured in O₂- and N₂-saturated acid electrolyte at two representative potentials (0.2 and 0.8 V vs. RHE) for Co_{0.5} and Fe_{0.5}, respectively. Although for Fe_{0.5} we do not observe significant spectral changes in O₂-free or O₂-saturated electrolyte, for Co_{0.5} a clear variation is observed between 7720 and 7735 eV. This effect is magnified in the experimental $\Delta\mu_{\text{O}_2\text{-N}_2}$ spectra obtained by subtracting from the XANES spectrum of Co_{0.5} measured under O₂ that measured under N₂ (insets of Fig. 4c, d). A fit of the $\Delta\mu_{\text{O}_2\text{-N}_2}$ spectrum of Co_{0.5} at 0.8 V is shown in Supplementary Fig. 9, corresponding to an active-site structure with four nitrogen atoms at 1.95 Å with or without an oxygen molecule adsorbed end-on at 2.22 Å. In N₂-saturated electrolyte, oxygen comes exclusively from water activation, whereas in O₂-saturated electrolyte the oxygen may come from water activation or O₂ adsorption. These $\Delta\mu$ analyses strongly suggest that, for Fe_{0.5}, an Fe-O bond probably exists in both O₂-saturated and N₂-saturated electrolytes, with oxygen originating from O₂ and H₂O, respectively. In contrast, for Co_{0.5} the active sites are less oxophilic and a Co-O bond is formed only in O₂-saturated electrolyte. To the best of our knowledge, this is the first direct *operando* evidence of molecular O₂ adsorption on the cobalt centers in Co-N-C materials. The general picture that emerges from the present work supports the

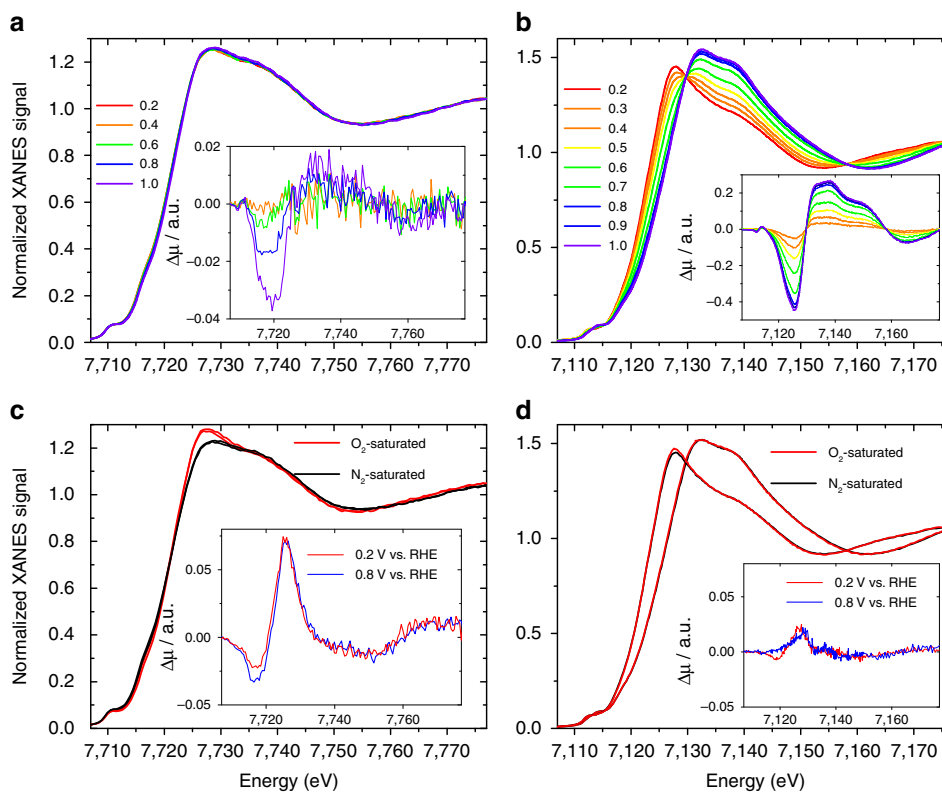


Fig. 4 Operando XANES spectra. Taken in 0.5 M H_2SO_4 for $\text{Co}_{0.5}$ (left) and $\text{Fe}_{0.5}$ (right). The spectra were measured as a function of the electrochemical potential in N_2 -saturated electrolyte for **a** $\text{Co}_{0.5}$ and **b** $\text{Fe}_{0.5}$ (legend for potentials is in V vs RHE) and measured as a function of the saturating gas (O_2 or N_2) at either 0.2 V vs. RHE or 0.8 V vs. RHE for **c** $\text{Co}_{0.5}$ and **d** $\text{Fe}_{0.5}$. Insets of **a** and **b** are differential $\Delta\mu$ XANES spectra obtained by subtracting the normalized spectrum at every potential to the spectrum recorded at 0.2 V vs. RHE. Insets of **c** and **d** are $\Delta\mu$ spectra obtained by subtracting the normalized XANES spectra recorded in O_2 - to that recorded in N_2 -saturated electrolyte, at a fixed potential

view that the active moieties formed at high temperature have a porphyrinic or defective porphyrinic architecture and also obey to the same general trends that have been reported on well-defined macrocycles comprising 3d transition-metal ions from the first row^{22, 26, 42, 43}. However, while cobalt moieties in pyrolyzed materials do not change structure when catalyzing the ORR in acid medium, the iron moieties do change structure due to the change of oxidation and/or the spin state. The exact structural change induced by the redox switch will require extensive modeling work, which is beyond the scope of the present paper. Last, while general reactivity trends seem to apply for both pyrolyzed Metal-N-C materials and well-defined metal macrocycles, this does not mean however that their absolute ORR activity and O_2 adsorption energy are the same. For example, the O_2 adsorption energy on the three porphyrinic-derived CoN_xC_y moieties in ground state is -0.80 to -1.26 eV (Supplementary Table 4), higher than that reported for cobalt phthalocyanines and porphyrins (-0.60 to -0.35 eV).⁴² The covalent integration of the Metal- N_x moieties in a conductive carbon matrix generally modifies the electron density at the metal relative to a metal macrocycle adsorbed on carbon.⁵⁰

Electroactivity of cobalt moieties for other reactions. After having identified the porphyrinic structure of three possible cobalt moieties in $\text{Co}_{0.5}$, we investigated their electrochemical activity for the OER, HER and HOR in acid medium. The cobalt moieties are the most active-site for OER in $\text{Co}_{0.5}$, as indicated by the significantly lower OER activity of N-C (purple vs. Gray curve in Supplementary Fig. 10). Due to the low density of cobalt

sites in $\text{Co}_{0.5}$, the OER potential at a current density of 2 mA cm^{-2} is however positively shifted by 200 mV relative to that of unsupported IrO_2 nanoparticles. While the OER activity of such cobalt moieties is interesting from a fundamental point of view, the low stability of carbon at such high electrochemical potential limits their practical application.⁵¹ The low current observed at 1.3–1.6 V vs. RHE on $\text{Co}_{0.5}$ might in fact entirely or partially originate from carbon corrosion, enhanced in the presence of cobalt relative to N-C. OER activity has been predicted from DFT theory for CoN_xC_y and FeN_xC_y moieties.⁵² In contrast to the case for ORR, the oxygen-binding energy of the porphyrinic $\text{CoN}_4\text{C}_{12}$ moiety is close to the ideal value that may be expected for a Metal- N_4 moiety.⁵² OER activity has also been reported experimentally for heterogeneous Co-N⁵²C materials in alkaline medium.²² These heterogeneous catalysts mostly comprised metallic cobalt or cobalt oxide while the presence of CoN_xC_y moieties could not be certified.^{53–55} The onset of OER in acidic medium on $\text{Co}_{0.5}$ is not well defined but clearly situated above the redox peak associated with Co(II)/Co(III) at 1.25 V vs. RHE (Supplementary Fig. 2), suggesting Co(III) N_xC_y moieties could be the active-site for OER in $\text{Co}_{0.5}$. The operando XANES spectra were also recorded at OER potentials, and these spectra showed only a small difference compared to the XANES spectrum recorded at 1.0 V vs. RHE (Supplementary Fig. 11), supporting the fact that CoN_xC_y moieties were still present at such high potential and are responsible for the OER activity of $\text{Co}_{0.5}$. As for the ORR, it must be noted that the cobalt content in $\text{Co}_{0.5}$ was not optimized to reach the highest activity.

In contrast, Co-N-C materials should be stable for long duration at low potentials needed to catalyze the HER. Two

recent reports demonstrated the high activity of CoN_xC_y moieties toward HER in acid and alkaline medium.^{28, 29} The HER polarization curve of $\text{Co}_{0.5}$ is however negatively shifted by 200 mV relative to Pt/C (Supplementary Fig. 12). In addition, $\text{Co}_{0.5}$ did not show any activity for the HOR (Supplementary Fig. 13), highlighting an irreversible behavior between HER and HOR on cobalt moieties. This intriguing fact seems to also apply to non-precious metal solid-state materials such as Mo and W nitrides, sulfides, and carbides. Such structures lead to efficient HER catalysts but were never reported to be efficient HOR catalysts.^{56, 57}

Discussion

We identified with XANES, EXAFS, magnetic susceptibility measurements and DFT analysis the detailed structures and electronic state of single-atom catalytic sites in pyrolyzed Co–N–C materials. Three (defective) porphyrinic moieties were identified and showed some activity toward the ORR, OER and HER in acidic medium. DFT-D calculations showed that these cobalt moieties likely bind oxygen intermediates too weakly relative to an optimum Metal–N–C ORR catalyst, while iron moieties bind oxygen intermediates more strongly than cobalt ones. It however cannot be determined from the present study if iron moieties bind oxygen intermediates more or less strongly than optimally desired for the ORR. These insights support that the general activity descriptors for the active sites in pyrolyzed Metal–N–C catalysts are similar to those identified earlier for molecular Metal–N₄ macrocycles. For Co–N–C catalysts, modifications of the carbon matrix with nitrogen or other light elements resulting in a stronger O₂ binding energy at cobalt centers should improve their ORR activity. Generally, rational modification of the carbon matrix hosting such metal-centered moieties could be used for optimizing their activity toward a large variety of (electro)chemical reactions. These materials can bridge the gap between molecular and solid-state catalytic materials, offering perspectives for catalysts based on earth-abundant elements.

Methods

Synthesis. The catalyst precursor of $\text{Co}_{0.5}$ was prepared from a Zn(II) zeolitic imidazolate framework (Basolite Z1200 from BASF, labeled ZIF-8), Co(II) acetate and 1,10-phenanthroline. Weighed amounts of the powders of Co(II)Ac (15.97 mg), phen (200 mg) and ZIF-8 (800 mg) were ball-milled (Pulverisette 7 premium, Fritsch) at 400 rpm for 2 h (4 × 30 min with 5 min rest in-between) in a ZrO₂ crucible (45 cm³) filled with 100 ZrO₂ balls (5 mm diameter). A split-hinge oven was equilibrated at 1,050 °C under Ar flow, and the catalyst precursor was quickly introduced and pyrolyzed at 1,050 °C in Ar for 1 h (see details in ref. 22). The N–C material was prepared similarly but without cobalt. Due to a mass loss of 65–70 wt % during pyrolysis in Ar (unmodified by the presence of Co or Fe at 0.5 wt%) caused by volatile products formed from ZIF-8 and phen while Co does not form volatile compounds, the cobalt content in $\text{Co}_{0.5}$ is 1.5 wt%.

Rotating ring disk electrode measurements. Electrochemical activity and selectivity toward the ORR was determined using the RRDE technique. For $\text{Co}_{0.5}$, N–C and Pt/C (5 wt% Pt/C, provided by Johnson Matthey) catalysts, an ink including 10 mg of catalyst, 109 μl of a 5C wt% Nafion[®] solution containing 15–20% water, 300 μl of ethanol and 36 μl of de-ionized water was sonicated and mixed using a vortex. An aliquot of 9 μl was deposited on the glassy-carbon disk (0.247 cm²) with a Pt ring (Pine Instruments, nominal collection efficiency 0.37), resulting in a loading of 818 μg·cm⁻². For lower $\text{Co}_{0.5}$ loadings (200 μg·cm⁻²), the catalyst mass and Nafion solution aliquot in the ink were proportionally decreased, and the decrease in Nafion solution balanced by increased ethanol aliquot. 9 μl of ink was again deposited on glassy carbon. The working electrode with the deposited catalyst layer was used in a four-electrode cell setup connected to a bipotentiostat (Biologic SP 300) and rotator (MSR, Pine Instruments). The counter and reference electrodes were a graphite rod and a reversible hydrogen electrode (RHE), respectively. The acidic electrolyte was an O₂-saturated aqueous solution of 0.1 M H₂SO₄, except for ORR on Pt/C (0.1 M HClO₄). For Pt/C only, the electrode was first cleaned by performing 300 cycles at 500 mV s⁻¹ between 0 and 1 V vs. RHE. The RDE polarization curves were recorded with a scan rate of 10 (Fe–N–C) or 50 mV s⁻¹ (Pt/C, to avoid contamination) at 1,600 r.p.m. and corrected for the

background current measured in N₂-saturated electrolyte. The second cycle was used for correction. For measuring the % H₂O₂ released during ORR, the potential of the Pt ring was held at 1.2 V vs. RHE.

Square-wave voltammetry. Catalysts inks were prepared by dispersing 3.1 mg catalyst in a solution prepared by mixing 150.2 μl of millipore water, 465 μl of isopropyl alcohol and 6.2 μl of 5 wt% Nafion[®] (Nafion to catalyst mass ratio of 10 wt%). The ink solution was then sonicated 60 min. 20 μl of the ink was pipetted on the glassy carbon disk (0.247 cm²) to reach a loading of 400 μg·cm⁻². This lower loading than used for most RRDE experiments was necessary to obtain a proper balance between the signal coming from the redox peak and that due to the double layer. The electrodes were dried through a rotational drying method at 800 r.p.m. SWV experiments were carried out in 0.1 M HClO₄ aqueous electrolyte using an Autolab bipotentiostat (PGSTAT302N) with a step potential of 5 mV, potential amplitude of 20 mV and scan frequency of 10 Hz in a standard electrochemical cell (Chemglass).

Fuel cell measurements. For the membrane electrode assembly, cathode inks were prepared using the following formulation: 20 mg of catalyst, 652 μl of a 5 wt% Nafion[®] solution containing 15–20% water, 326 μl of ethanol and 272 μl of de-ionized water. The inks were alternatively sonicated and agitated with a vortex mixer every 15 min, for a total of 1 h. Then, three aliquots of 405 μl of the catalyst ink were successively deposited on the microporous layer of an uncatalysed 4.84 cm² gas diffusion layer (Sigracet S10-BC) to reach a catalyst loading of 4 mg·cm⁻². The cathode was then placed in a vacuum oven at 80 °C to dry for 2 h. The anode used for all PEM fuel cell tests performed in this work was 0.5 mg_{Pt}·cm⁻² on Sigracet S10-BC. Assemblies were prepared by hot-pressing 4.84 cm² anode and cathode against either side of a Nafion NRE-211 membrane at 135 °C for 2 min. PEMFC tests were performed with a single-cell fuel cell with serpentine flow field (Fuel Cell Technologies Inc.) using an in-house fuel cell bench and a Biologic Potentiostat with a 50 A load and EC-Lab software. For the tests, the fuel cell temperature was 80 °C, the humidifiers were set at 85 °C, and the inlet pressures were set to 1 bar gauge for both anode and cathode sides. The flow rates for humidified H₂ and O₂ were controlled downstream of the polymer electrolyte membrane fuel cell (PEMFC) and fixed at 50 s.c.c.m. Polarization curves were recorded by scanning the cell voltage at 0.5 mV s⁻¹.

Spectroscopic experimental characterization. Co and Fe K-edge X-ray absorption spectra were collected at room temperature at SAMBA beamline (Synchrotron SOLEIL) equipped with a double crystal Si 220 monochromator. Catalyst inks were prepared by mixing 10 mg catalyst with 50 μl de-ionized water and 100 μl of 5 wt% Nafion[®] solution with ultrasounds. A 50 μl aliquot was then pipetted on ~3 cm² circular area of a 100-μm-thick graphite foil (Goodfellow cat. C 000200/2), resulting in a catalyst loading of ~1 mg·cm⁻². The graphite foil then served as a working electrode, and was installed in an electrochemical cell (PECC2, from Zahner), see Supplementary Fig. 14. The cell also includes a reference Ag/AgCl electrode, and a Pt counter electrode. The cell was filled with a given electrolyte and saturated with either O₂ or N₂ by continuously bubbling gas in the electrolyte. *Operando* measurements were performed by recording the K_α X-ray fluorescence of the element under study (Co or Fe) with a Canberra 35-elements monolithic planar Ge pixel array detector, while the ex situ spectra of the reference compound Co(II)Pc and $\text{Co}_{0.5}$ were recorded in transmission geometry on pelletized disks of 10 mm diameter with 1 mm thickness, using Teflon powder (1 μm particle size) as a binder.

Spectroscopic analysis and modeling. The EXAFS data analysis was performed with the GNXAS code^{58, 59}. In that approach the interpretation of the experimental data is based on the decomposition of the EXAFS $\chi(k)$ signal (defined as the oscillation with respect to the atomic background cross-section normalized to the corresponding K-edge channel cross-section) into a summation over n-body distribution functions $\gamma^{(n)}$ calculated by means of the multiple-scattering (MS) theory. The cobalt first coordination shells have been modeled with Γ -like distribution functions which depend on four parameters, namely, the coordination number N, the average distance R, the mean-square variation σ^2 and the skewness β . Note that β is related to the third cumulant C₃ through the relation C₃ = $\sigma^3\beta$. The standard deviations given for the refined parameters in Supplementary Table 1 are obtained from k²-weighted least-squares refinements of the EXAFS function $\chi(k)$, and do not include systematic errors of the measurements. Least-square fits of the EXAFS raw experimental data have been performed by minimizing a residual function of the type:

$$R_i(\{\lambda\}) = \sum_{i=1}^N \frac{[\alpha_{\text{exp}}(E_i) - \alpha_{\text{mod}}(E_i; \lambda_1, \lambda_2, \dots, \lambda_p)]^2}{\sigma_i^2}, \quad (1)$$

where N is the number of experimental points, $E_i\{\lambda\} = (\lambda_1, \lambda_2, \dots, \lambda_p)$ are the p parameters to be refined and σ_i^2 is the variance associated with each experimental point $\alpha_{\text{exp}}(E_i)$. Additional non-structural parameters were minimized, namely E₀

(core ionization threshold energy) and S_0^2 (amplitude reduction factor taking into account intrinsic losses).

The XANES data analysis of $\text{Co}_{0.5}$ was carried out with the MXAN code in the framework of the full MS scheme, following the same modeling approach applied to identify the structure of the catalytic active sites in Fe–N–C materials²². The MXAN method is based on the MT approximation for the shape of the potential and uses a complex optical potential, based on the local density approximation of the self-energy of the excited photoelectron⁶⁰. The minimization of the Co(II)Pc XANES spectrum has been carried out starting from the X-ray structure of this compound⁴⁷, while in the case of $\text{Co}_{0.5}$ we tested different coordination geometries. The cluster size used in the calculations was chosen on the basis of a convergence criterion. The fit includes a minimal number of selected parameters: the Co–N and Co–O distances, the Co-displacement, the Co-5th ligand distance and the bending angle between the Co–O vector and the O–O bond. During the fit, the outer carbon atoms of the ring rigidly followed the motion of the nitrogen atoms. Least-square fits of the experimental data in the space of the structural parameters were achieved by minimizing the residual function defined as

$$R_{sq} = \frac{n}{\sum_{i=1}^m w_i} \sum_{i=1}^m \frac{w_i (y_i^{\text{th}} - y_i^{\text{exp}})^2}{\epsilon_i^2}, \quad (2)$$

where n is the number of independent parameters, m is the number of data points, y_i^{th} and y_i^{exp} are the theoretical and experimental values of absorption, respectively, ϵ_i is the individual error in the experimental data set, and w_i is a statistical weight. Here, we assumed a constant experimental error, $\epsilon = 1.2\%$, for the whole experimental data set. Five non-structural parameters have been optimized, namely the Fermi energy level E_F , the experimental resolution Γ_{exp} , the threshold energy E_0 and energy and amplitude of the plasmon, E_s and A_s . The fit of the $\Delta\mu$ XANES spectrum of $\text{Co}_{0.5}$ in O_2^- or N_2 -saturated electrolyte was obtained by the MXAN code with the following procedure: (1) Theoretical XANES spectrum calculation of the $\text{CoN}_4\text{C}_{12}$ moiety as reference, using the spectrum under nitrogen at 0.8 V. (2) At each step of the fitting procedure the program calculated the theoretical spectrum of a $\text{CoN}_4\text{C}_{12}\text{-O}_2$ moiety under oxygen. (3) The difference spectrum is calculated.

DFT-D computation. DFT-D computations were carried out on cluster models shown in Supplementary Fig. 6. The dangling bonds were saturated with hydrogen. The computational method is based on the DFT cluster approach augmented with an empirical dispersion term as implemented in deMon2k computer program used for the present computations⁶¹. For the exchange-correlation functional, the approximations of Perdew–Burke–Ernzerhof's 1996 was used⁶². Triple- ζ basis sets were used for the C and H atoms and double- ζ bases plus polarization for Co(II) cations⁶³. Automatically generated auxiliary functions up to $l=2$ (for the metal atom) and 3 (for H, C and O atoms) were used for fitting the density. A quasi-Newton method in internal redundant coordinates with analytical energy gradients was used for structure optimization. The convergence was based on the Cartesian gradient and displacement vectors with thresholds of 10^{-3} a.u. The energy convergence was set to 10^{-7} a.u. The binding energy of cobalt cation per Co–N bond (BE) and adsorption energy of end-on adsorbed O_2 molecule (E_{ads}) are obtained as

$$BE = E_{\text{tot}}[\text{complex}] - E_{\text{tot}}(\text{Co(II)}) - E_{\text{tot}}[(\text{N}_4\text{C}_y)^{2-}]. \quad (3)$$

$$E_{\text{ads}} = E_{\text{tot}}[\text{O}_2/\text{complex}] - E[\text{O}_2] - E[\text{complex}]$$

In the above formula, the total energies for the ground state triplet dioxygen with total spin $S=1$ (two unpaired electrons) and Co^{2+} in its quartet ground state (total spin $S=3/2$) were used. The relative energies ΔE with spin number are obtained as a difference between the total energies of the higher-energy minima states and the ground state. The atomic spin density was computed for all the minima energy structures using Mulliken⁶⁴ and Hirshfeld⁶⁵ population analysis. Both population schemes led to nearly identical results. Cobalt divalent cations were used. The relative energies ΔE with spin number are obtained as a difference between the total energies of the higher-energy minima states and the ground state.

SQUID measurements. The molar magnetic susceptibility χ_m was measured from 2 to 300 K for $\text{Co}_{0.5}$ and N–C with a Superconducting QUantum Interference Device (SQUID) (MPMS XL-7T, Quantum Design) at a magnetic field of 5,000 Oe. A mass of 16 mg of $\text{Co}_{0.5}$ or N–C was weighed and introduced in a polymer straw. The average effective magnetic moment of cobalt atoms (μ_{eff}) was then obtained by fitting the plot of $1/\chi_m$ (in mol of cobalt atoms per emu) vs. $1/T$ with a linear law in the region 15–77 K. The value for the slope obtained is defined as a $1/C_m$. From the C_m -value, the average effective magnetic moment of cobalt atoms (μ_{eff}) is directly calculated via the relation $\mu_{\text{eff}} = 2.82 \cdot C_m^{1/2}$, in units of Bohr magneton (μ_B).

The average spin of cobalt ions is then obtained via $\mu_S = g \cdot \mu_B \cdot \text{sqrt}(s(s+1))$, where g is equal to 2.002 and s is the average spin density for all cobalt moieties present in $\text{Co}_{0.5}$.

TEM measurements. For transmission electron microscopy (TEM), the sample powders were dispersed in ethanol using an ultrasonic bath and deposited onto holey-carbon grids. TEM imaging and SAED were carried out on a JEM-2100HCKM microscope (JEOL Ltd., Japan) operating at 120 keV.

Data availability. The data that support the findings of this study are available from the corresponding authors upon reasonable request. The X-ray absorption Spectroscopy raw data associated with this work is permanently stored at SOLEIL and available upon request.

Received: 22 February 2017 Accepted: 17 August 2017

Published online: 16 October 2017

References

- Jacobson, M. Z., Colella, W. G. & Golden, D. M. Cleaning the air and improving health with hydrogen fuel-cell vehicles. *Science* **308**, 1901–1905 (2005).
- Debe, M. K. Electrocatalyst approaches and challenges for automotive fuel cells. *Nature* **486**, 43–51 (2012).
- Wagner, F. T., Lakshmanan, B. & Mathias, M. F. Electrochemistry and the future of the automobile. *J. Phys. Chem. Lett.* **1**, 2204–2219 (2010).
- Katsounaros, I., Cherevko, S., Zeradjanin, A. R. & Mayrhofer, K. J. J. Oxygen electrochemistry as a cornerstone for sustainable energy conversion. *Angew Chem. Int. Ed. Engl.* **53**, 102–121 (2014).
- Jasinski, R. A New fuel cell cathode catalyst. *Nature* **201**, 1212–1213 (1964).
- Gupta, S., Tryk, D., Bae, I., Aldred, W. & Yeager, E. Heat-treated polyacrylonitrile-based catalysts for oxygen electroreduction. *J. Appl. Electrochem.* **19**, 19–27 (1989).
- Chung, H. T., Won, J. H. & Zelenay, P. Active and stable carbon nanotube/nanoparticle composite electrocatalyst for oxygen reduction. *Nat. Commun.* **4**, 1922 (2012).
- He, Q. et al. Electrochemical and spectroscopic study of novel Cu and Fe-based catalysts for oxygen reduction in alkaline media. *J. Power Sources* **213**, 169–179 (2012).
- Jaouen, F. et al. Recent advances in non-precious metal catalysis for oxygen-reduction reaction in polymer electrolyte fuel cells. *Energy Environ. Sci.* **4**, 114–130 (2011).
- Proietti, E. et al. Iron-based cathode catalyst with enhanced power density in polymer electrolyte membrane fuel cells. *Nat. Commun.* **2**, 416 (2011).
- Wu, G., More, K. L., Johnston, C. M. & Zelenay, P. High-performance electrocatalysts for oxygen reduction derived from polyaniline, iron, and cobalt. *Science* **332**, 443–447 (2011).
- Lefèvre, M., Proietti, E., Jaouen, F. & Dodelet, J.-P. Iron-based catalysts with improved oxygen reduction activity in polymer electrolyte fuel cells. *Science* **324**, 71–74 (2009).
- Charreteur, F., Jaouen, F., Ruggeri, S. & Dodelet, J.-P. Fe/N/C non-precious catalysts for PEM fuel cells: influence of the structural parameters of pristine commercial carbon blacks on their activity for oxygen reduction. *Electrochim. Acta* **53**, 2925–2938 (2008).
- Zhang, R. et al. Fabrication of the pyrolyzing carbon-supported cobalt–dicyandiamide electrocatalysts and study on the active sites and mechanism for oxygen reduction in alkaline electrolyte. *J. Solid State Electrochem.* **19**, 1695–1707 (2015).
- Ramaswamy, N., Tylus, U., Jia, Q. & Mukerjee, S. Activity descriptor identification for oxygen reduction on nonprecious electrocatalysts: linking surface science to coordination chemistry. *J. Am. Chem. Soc.* **135**, 15443–15449 (2013).
- Kramm, U. I. et al. Structure of the catalytic sites in Fe/N/C-catalysts for O_2 -reduction in PEM fuel cells. *Phys. Chem. Chem. Phys.* **14**, 11673–11688 (2012).
- Tributsch, H., Koslowski, U. I. & Dorbandt, I. Experimental and theoretical modeling of Fe-, Co-, Cu-, Mn-based electrocatalysts for oxygen reduction. *Electrochim. Acta* **53**, 2198–2209 (2008).
- Liu, W. et al. Single-atom dispersed Co–N–C catalyst: structure identification and performance for hydrogenative coupling of nitroarenes. *Chem. Sci.* **7**, 5758–5764 (2016).
- Srinivasu, K. & Ghosh, S. K. Transition metal decorated graphyne: an efficient catalyst for oxygen reduction reaction. *J. Phys. Chem. C* **117**, 26021–26028 (2013).

20. Kattel, S. & Wang, G. A density functional theory study of oxygen reduction reaction on Me-N₄ (Me=Fe, Co, or Ni) clusters between graphitic pores. *J. Mater. Chem. A* **1**, 10790–10797 (2013).
21. Calle-Vallejo, F., Martínez, J. I. & Rossmeisl, J. Density functional studies of functionalized graphitic materials with late transition metals for oxygen reduction reactions. *Phys. Chem. Chem. Phys.* **13**, 15639–15643 (2011).
22. Zitolo, A. et al. Identification of catalytic sites for oxygen reduction in iron- and nitrogen-doped graphene materials. *Nat. Mater.* **14**, 937–942 (2015).
23. Kramm, U. I. et al. Effect of iron-carbide formation on the number of active sites in Fe-N-C catalysts for the oxygen reduction reaction in acidic media. *J. Mater. Chem. A* **2**, 2663–2670 (2014).
24. Jia, Q. et al. Spectroscopic insights into the nature of active sites in iron-nitrogen-carbon electrocatalysts for oxygen reduction in acid. *Nano Energy* **29**, 65–82 (2016).
25. Tylus, U. et al. Elucidating oxygen reduction active sites in pyrolyzed metal-nitrogen coordinated non-precious-metal electrocatalyst systems. *J. Phys. Chem. C* **118**, 8999–9008 (2014).
26. Li, J. et al. Structural and mechanistic basis for the high activity of Fe-N-C catalysts toward oxygen reduction. *Energy Environ. Sci.* **9**, 2418–2432 (2016).
27. Goellner, V., Armel, V., Zitolo, A., Fonda, E. & Jaouen, F. Degradation by hydrogen peroxide of metal-nitrogen-carbon catalysts for oxygen reduction. *J. Electrochem. Soc.* **162**, H403–H414 (2015).
28. Liang, H.-W. et al. Molecular metal-N_x centres in porous carbon for electrocatalytic hydrogen evolution. *Nat. Commun.* **6**, 7992 (2015).
29. Fei, H. et al. Atomic cobalt on nitrogen-doped graphene for hydrogen generation. *Nat. Commun.* **6**, 8668 (2015).
30. Lefèvre, M., Dodelet, J. P. & Bertrand, P. Molecular oxygen reduction in PEM fuel cell conditions: ToF-SIMS analysis of Co-based electrocatalysts. *J. Phys. Chem. B* **109**, 16718–16724 (2005).
31. Kattel, S., Atanassov, P. & Kiefer, B. Catalytic activity of Co-N_x/C electrocatalysts for oxygen reduction reaction: a density functional theory study. *Phys. Chem. Chem. Phys.* **15**, 148–153 (2012).
32. Liu, K., Kattel, S., Mao, V. & Wang, G. Electrochemical and computational study of oxygen reduction reaction on nonprecious transition metal/nitrogen doped carbon nanofibers in acid medium. *J. Phys. Chem. C* **120**, 1586–1596 (2016).
33. Li, F. et al. Atomic mechanism of electrocatalytically active Co-N complexes in graphene basal plane for oxygen reduction reaction. *ACS Appl. Mater. Interfaces* **7**, 27405–27413 (2015).
34. Chen, X., Li, F., Zhang, N., An, L. & Xia, D. Mechanism of oxygen reduction reaction catalyzed by Fe(Co)-N_x/C. *Phys. Chem. Chem. Phys.* **15**, 19330–19336 (2013).
35. Ziegelbauer, J. M. et al. Direct spectroscopic observation of the structural origin of peroxide generation from Co-based pyrolyzed porphyrins for ORR applications. *J. Phys. Chem. C* **112**, 8839–8849 (2008).
36. Zhang, H.-J., Yuan, X., Ma, Z.-F., Wen, W. & Yang, J. Investigation of non-precious metal CoN₄-based oxygen reduction catalyst by electrochemical and X-ray absorption spectroscopy techniques. *J. Electrochem. Soc.* **161**, H155–H160 (2014).
37. Kobayashi, M. et al. Role of residual transition-metal atoms in oxygen reduction reaction in cobalt phthalocyanine-based carbon cathode catalysts for polymer electrolyte fuel cell. *J. Power Sources* **196**, 8346–8351 (2011).
38. Sun, S., Jiang, N. & Xia, D. Density functional theory study of the oxygen reduction reaction on metalloporphyrins and metallophthalocyanines. *J. Phys. Chem. C* **115**, 9511–9517 (2011).
39. Li, C. et al. Efficient oxygen electroreduction over ordered mesoporous Co-N-doped carbon derived from cobalt porphyrin. *RSC Adv.* **6**, 15167–15174 (2016).
40. Yang, Y. et al. Porous cobalt, nitrogen-codoped carbon nanostructures from carbon quantum dots and VB12 and their catalytic properties for oxygen reduction. *Phys. Chem. Chem. Phys.* **16**, 25350–25357 (2014).
41. Jaouen, F. in *Non-Noble Metal Fuel Cell Catalysts* (eds Chen, Z., Dodelet, J.-P. & Dodelet, J. Z.) 29–118 (Wiley-VCH Verlag GmbH & Co. KGaA, 2014).
42. Zagal, J. H. & Koper, M. T. M. Reactivity descriptors for the activity of molecular MN₄ catalysts for the oxygen reduction reaction. *Angew. Chem. Int. Ed. Engl.* **55**, 14510–14521 (2016).
43. Jia, Q. et al. Experimental observation of redox-induced Fe-N switching behavior as a determinant role for oxygen reduction activity. *ACS Nano* **9**, 12496–12505 (2015).
44. Parthasarathy, A., Srinivasan, S., Appleby, A. J. & Martin, C. R. Pressure dependence of the oxygen reduction reaction at the platinum microelectrode/nafton interface: electrode kinetics and mass transport. *J. Electrochem. Soc.* **139**, 2856–2862 (1992).
45. Gottesfeld, S. in *Fuel Cell Catalysis* (ed. Koper, T. M.) 1–30 (John Wiley & Sons, Inc., 2009).
46. Jaouen, F. & Dodelet, J.-P. Average turn-over frequency of O₂ electro-reduction for Fe/N/C and Co/N/C catalysts in PEFCs. *Electrochim. Acta.* **52**, 5975–5984 (2007).
47. Mason, R., Williams, G. A. & Fielding, P. E. Structural chemistry of phthalocyaninato-cobalt(II) and -manganese(II). *J. Chem. Soc. Dalton Trans.* 676–683 (1979).
48. Wang, Z., Lee, M., Choi, E. S., Poston, J. & Seehra, M. S. Low temperature, high magnetic field investigations of the nature of magnetism in the molecular semiconductor β-cobalt phthalocyanine (C₃₂H₁₆CoN₈). *J. Magn. Magn. Mater.* **407**, 83–86 (2016).
49. Briois, V., Sainctavit, P., Long, G. J. & Grandjean, F. Importance of photoelectron multiple scattering in the iron K-Edge X-ray absorption spectra of spin-crossover complexes: full multiple scattering calculations for several iron(II) trispyrazolylborate and trispyrazolylmethane complexes. *Inorg. Chem.* **40**, 912–918 (2001).
50. Calle-Vallejo, F., Martínez, J. I., Garcia-Lastra, J. M., Abad, E. & Koper, M. T. M. Oxygen reduction and evolution at single-metal active sites: comparison between functionalized graphitic materials and protoporphyrins. *Surf. Sci.* **607**, 47–53 (2013).
51. Goellner, V. et al. Degradation of Fe/N/C catalysts upon high polarization in acid medium. *Phys. Chem. Chem. Phys.* **16**, 18454–18462 (2014).
52. Busch, M. et al. Beyond the top of the volcano?—a unified approach to electrocatalytic oxygen reduction and oxygen evolution. *Nano Energy* **29**, 126–135 (2016).
53. Chao, S. & Geng, M. 3,5-Diamino-1,2,4-triazole as a nitrogen precursor to synthesize highly efficient Co-N/C non-precious metal bifunctional catalyst for oxygen reduction reaction and oxygen evolution reaction. *Int. J. Hydrogen Energy* **41**, 12995–13004 (2016).
54. Qiao, X. et al. Cobalt and nitrogen codoped graphene with inserted carbon nanospheres as an efficient bifunctional electrocatalyst for oxygen reduction and evolution. *ACS Sustain. Chem. Eng.* **4**, 4131–4136 (2016).
55. Zhang, X. et al. Co/CoO nanoparticles immobilized on Co-N-doped carbon as trifunctional electrocatalysts for oxygen reduction, oxygen evolution and hydrogen evolution reactions. *Chem. Commun.* **52**, 5946–5949 (2016).
56. Kibsgaard, J., Chen, Z., Reinecke, B. N. & Jaramillo, T. F. Engineering the surface structure of MoS₂ to preferentially expose active edge sites for electrocatalysis. *Nat. Mater.* **11**, 963–969 (2012).
57. Merki, D. & Hu, X. Recent developments of molybdenum and tungsten sulfides as hydrogen evolution catalysts. *Energy Environ. Sci.* **4**, 3878–3888 (2011).
58. Filipponi, A., Di Cicco, A. & Natoli, C. R. X-ray-absorption spectroscopy and n-body distribution functions in condensed matter. I. Theory. *Phys. Rev. B* **52**, 15122–15134 (1995).
59. Filipponi, A. & Di Cicco, A. X-ray-absorption spectroscopy and n-body distribution functions in condensed matter. II. Data analysis and applications. *Phys. Rev. B* **52**, 15135–15149 (1995).
60. Benfatto, M. & Della Longa, S. Geometrical fitting of experimental XANES spectra by a full multiple-scattering procedure. *J. Synchrotron. Radiat.* **8**, 1087–1094 (2001).
61. Geudtner, G. et al. deMon2k. Wiley Interdiscip. Rev. Comput. Mol. Sci. **2**, 548–555 (2012).
62. Perdew, J. P., Burke, K. & Ernzerhof, M. Generalized gradient approximation made simple. *Phys. Rev. Lett.* **77**, 3865–3868 (1996).
63. Goubout, N., Salahub, D. R., Andzelm, J. & Wimmer, E. Optimization of gaussian-type basis sets for local spin density functional calculations. Part I. boron through neon, optimization technique and validation. *Can. J. Chem.* **70**, 560–571 (1992).
64. Mulliken, R. S. Electronic population analysis on LCAO-MO molecular wave functions. I. *J. Chem. Phys.* **23**, 1833–1840 (1955).
65. Hirshfeld, F. L. Bonded-atom fragments for describing molecular charge densities. *Theor. Chim. Acta.* **44**, 129–138 (1977).

Acknowledgements

This research was supported by ANR under contract 2011 CHEX 004 01 and by the Project 'PEMFC-SUDO'E' -SOE1/P1/E0293 which is co-financed by the European Regional Development Fund in the framework of the Interreg Sudoe programme. We also acknowledge Synchrotron SOLEIL (Gif-sur Yvette, France) for provision of synchrotron radiation facilities at beamline SAMBA (proposal numbers 20120701 and 20150913), Valérie Briois for valuable discussions and Álvaro Reyes-Carmona (formerly at Université Montpellier, now at ICIQ, Spain) for sharing the benchmark IrO₂ polarization curve.

Author contributions

A.Z. participated in the XAS measurements and performed the XAS data analysis. N.R.-S. conducted the catalyst synthesis and electrochemical studies and participated in XAS measurements, T.M. conducted the DFT analysis. J.L. performed the SWV experiments. Q.J. and S.M. contributed to the data interpretation and manuscript writing. S.S., P.K. and E.F. participated in the XAS data acquisitions and contributed to the data

interpretation. G.F.H. and S.L. performed the TEM characterization. F.J. and A.Z. supervised the project, wrote and edited the manuscript, with inputs from all authors.

Additional information

Supplementary Information accompanies this paper at doi:[10.1038/s41467-017-01100-7](https://doi.org/10.1038/s41467-017-01100-7).

Competing interests: The authors declare no competing financial interests.

Reprints and permission information is available online at <http://npg.nature.com/reprintsandpermissions/>

Publisher's note: Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

© The Author(s) 2017